



Original Article

Study on Preparation of Ag - SiO₂ Nanocomposite Material Enhancing Fluorescence for Rhodamine 6G

Bui Van Hong, Hoang Chi Hieu*, Nguyen Thi Bao Yen

VNU University of Science, 334 Nguyen Trai, Thanh Xuan, Hanoi, Vietnam

Received 8th October 2025

Revised 10th November 2025; Accepted 28th April 2026

Abstract: Ag - SiO₂ nanocomposite material was synthesized by the Stöber method and reduction process. SEM images showed that SiO₂ in the form of a nanosphere, and an average particle size of 165 nm, and Ag nanoparticles possess an average particle size of 17 nm, distributed quite evenly on the surface of SiO₂ nanospheres. The UV - Vis absorption spectrum of Ag - SiO₂ material presents a broad band at 400 nm attributed to plasmon surface resonance of Ag nanoparticles. Mixing up solutions of Ag - SiO₂ and R6G, a fluorescence band of Rhodamine 6G (R6G) at 570 nm increased 86 times compared with that of only R6G. The as-prepared Ag - SiO₂ nanocomposite material also increased the fluorescence intensity of R6G with concentration varying from 0.1 to 100 ppm.

Keywords: Ag - SiO₂, Rhodamine 6G, MEF, photoluminescence, fluorescence.

1. Introduction

SiO₂ possesses thermal stability, chemical inertness, and non-toxic properties. Moreover, the nano-structure of SiO₂ can easily be fabricated into nanoparticles and uniformly dispersed in various solutions. Due to its high biocompatibility and functionalized surface, it can readily bond with metals [1]. Meanwhile, the surface plasmon resonance (SPR) of Ag nanoparticles around 400 nm, can generate enhanced fluorescence with dyes [2]. Experimental and theoretical studies have shown that enhancement fluorescence is dependent on multiple factors, such as the type, size, and shape of metal, the metal-fluorophore distance, the radiative decay rate, and the quantum yield of the fluorophore, as well as the overlap of the absorption and emission bands of the fluorophore with the metal's plasmon band [3]. Ag - SiO₂ nanostructures have been successfully synthesized through various methods, allowing control over the morphology and size of Ag - SiO₂, which in turn affects the material's Metal-Enhanced-

* Corresponding author.

E-mail address: hieuhc@hus.edu.vn

<https://doi.org/10.25073/2588-1124/vnumap.5085>

Fluorescence (MEF) capabilities [4]. Ag - SiO₂ material has been shown to significantly enhance the fluorescence of various dyes such as crystal violet, methylene blue, malachite green (MG), and especially Rhodamine 6G (R6G)- an organic dye widely used in industry [5]. However, a critical aspect that the previous studies have not thoroughly investigated the role of Ag concentration on the MEF ability of Ag - SiO₂ material. In this report, we study the changing amount of Ag nanoparticles attached to SiO₂nanospheres by altering the concentration of AgNO₃ in Ag - SiO₂ synthesis process, to investigate the MEF of Ag - SiO₂ material for Rhodamine 6G (R6G).

2. Experimental

Tetraethoxysilane Si(OC₂H₅)₄ (99.98%), (3-aminopropyl) trimethoxysilane H₂N(CH₂)₃Si(OCH₃)₃ (99.96%), silver nitrate AgNO₃ (99.99%), sodium borohydride (NaBH₄), ammonia NH₃ (25%), Rhodamine 6G (R6G), and absolute ethanol were purchased from Sigma Aldrich, China. All chemicals used were of analytical grade. Deionized (DI) water was utilized in all experiments.

SiO₂ nanospheres were synthesized by the Stöber method from tetraethyl orthosilicate (TEOS), NH₃, and absolute ethanol. The Ag-coated SiO₂ nanoparticles were synthesized through the following steps: 0.1 g of SiO₂ was dissolved in ethanol, and then 3-aminopropyl trimethoxysilane (APTMS) was added, with continuous magnetic stirring. The resulting precipitate was centrifuged and washed to obtain the white precipitate. Subsequently, 0.1 g of AgNO₃ was dissolved in 10 ml of water, followed by the addition of 3 ml NH₃. The above white precipitation was added to the AgNO₃ solution and a solution of 0.01g NaBH₄ in 10 ml DI water, and stirred further. The as Ag - SiO₂ solution was centrifuged, then dried at 80°C to yield Ag - SiO₂ in powder form. The Ag - SiO₂ were synthesized with concentrations of AgNO₃ of 0.1, 0.0125, 0.003125 mol/l (denoted as M₁, M₂, M₃).

The process to investigate the MEF of Ag - SiO₂ material for the R6G was conducted as follows: the Ag - SiO₂ solution (0.01 g/10 ml) and R6G solution (0.001 g/10 ml) were mixed together in a 3:1 volume ratio to create mixture A. Mixture A was then deposited on the Si substrate, and let them dry naturally.

The microstructure and morphology of Ag - SiO₂ material were analyzed by using X-ray diffraction (XRD) spectra obtained from the PANalytical Empyrean instrument with CuK α radiation ($\lambda = 1.54056$ Å, $2\theta = 10\div 70^\circ$) and nano scanning electron microscope Nova nanoSEM NPE199. Absorption spectra were recorded using the UV-2450 absorption spectrometer. Photoluminescence spectra were excited by 325 nm radiation from a He-Cd laser and recorded on the Spectra Pro2500i spectrometer.

3. Results and Discussion

3.1. Structure and Morphology of Ag - SiO₂ Material

Figure 1 shows the XRD patterns of Ag - SiO₂ material as varying the concentrations of AgNO₃, ranging from 0.1 to 0.003125 mol/l. The XRD pattern of Ag-SiO₂ using AgNO₃ at a concentration of 0.1 mol/l presents three diffraction peaks at 2θ angles of 38.00°, 44.24°, and 64.37°, respectively corresponding to the (110), (200), and (220) planes. These peaks are assigned to the face-centered cubic (fcc) structure of Ag [2, 8]. Additionally, a broad band near $2\theta \approx 24.5^\circ$ indicates the presence of the amorphous structure of SiO₂ [2, 8]. As the AgNO₃ concentration decreases, the characteristic Ag peaks remain at nearly the same 2θ positions, but their intensities progressively decrease (Figures 1b and 1c).

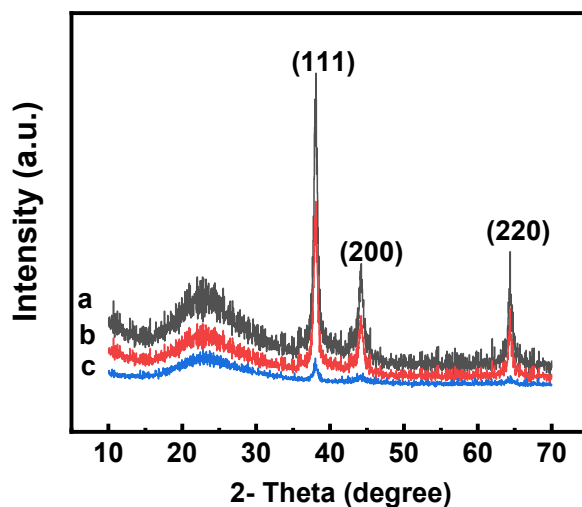


Figure 1. XRD patterns of Ag - SiO₂ material at different AgNO₃ concentrations: 0.1 mol/l (a), 0.0125 mol/l (b), and 0.003125 mol/l (c).

From the XRD pattern and using the Debye-Scherrer formula: $D = \frac{0.9\lambda}{\beta \cos\theta}$ where D is the average crystallite size, λ is the X-ray wavelength (1.5406 Å), β is the full width at half maximum (FWHM) of the diffraction peak, and θ is the Bragg diffraction angle, the crystallite sizes of Ag nanoparticles at different AgNO₃ concentrations were calculated to be approximately 16 nm.

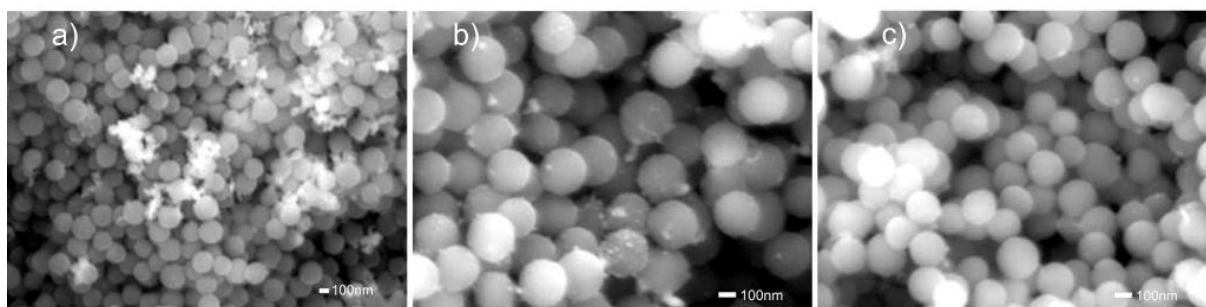


Figure 2. SEM images of Ag - SiO₂ material at different AgNO₃ concentrations: 0.1 mol/l (a), 0.0125 mol/l (b), and 0.003125 mol/l (c).

SEM images of Ag - SiO₂ material at varying concentrations of AgNO₃, from 0.1M to 0.003125M showed that Ag nanoparticles have successfully attached to the surface of the SiO₂ nanospheres. As the concentrations of AgNO₃ were reduced, the density of Ag nanoparticles attached to the SiO₂ surface progressively decreased.

3.2. UV-Vis Absorption Spectrum of Ag - SiO₂ Material

Figure 3 shows the UV-Vis absorption spectra of Ag - SiO₂ materials as the concentration of AgNO₃ was varied from 0.1 to 0.003125 M.

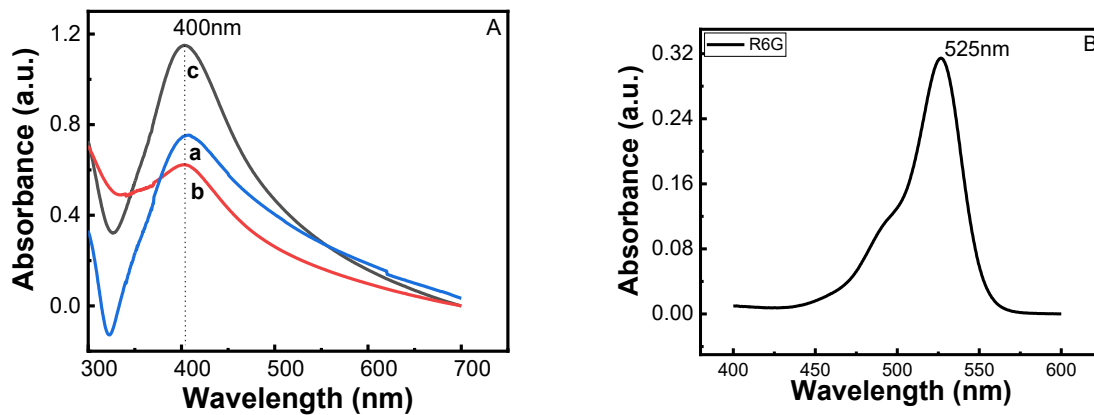


Figure 3. A. The UV-Vis absorption spectra of Ag - SiO₂ nanoparticles synthesized with varying AgNO₃ concentrations: M₁ (a), M₂ (b), M₃ (c) and B. The UV-Vis absorption spectrum of R6G.

The spectra display a Gaussian-like symmetrical absorption peak, indicating that Ag - SiO₂ possesses a nearly spherical shape with a narrow size distribution [6]. In sample M₁, a broad absorption band appears with a maximum at 400 nm, characteristic of the surface plasmon resonance (SPR) of Ag nanoparticles [7, 8]. When the concentration of AgNO₃ changes, the position of the surface plasmon absorption band of Ag remains almost unchanged, but the intensity of the band varies, as shown in Figure 3. This suggests that the AgNO₃ concentration affects the density of Ag nanoparticles decorating on SiO₂ nanospheres. Additionally, the UV-Vis spectrum of Rhodamine 6G (fig 3d) shows an absorption peak at 525 nm, corresponding to the monomer absorption band of R6G [9, 10].

3.3. Metal Enhanced Fluorescence Spectra of R6G Using Ag-SiO₂ Material

Figure 4 presents the MEF spectra of Ag - SiO₂ material with an AgNO₃ concentration of 0.0125 mol/l. The photoluminescence (PL) spectrum of Ag-SiO₂ material exhibits a weak PL peak at 430 nm, which is attributed to defects in the SiO₂ nanospheres (Figure 4a). Meanwhile, the PL spectrum of Rhodamine 6G (R6G) reveals two extremely weak peaks at 440 and 559 nm. Notably, when using Ag-SiO₂ material (M3) (Figure 4c), the 559 nm peak of R6G was enhanced by 2.4 times compared to the case without Ag - SiO₂. This demonstrates that Ag - SiO₂ effectively enhances the photoluminescence of R6G, indicating its potential application in fluorescence enhancement. The MEF effect requires a distance between the fluorophore and the metal nanostructure of about 10-20 nm. At low Ag concentrations, this distance is optimal for the most effective fluorescence enhancement. At the AgNO₃ concentration of 0.003125 mol/l (M3), the distance between R6G and the Ag particles is optimal, hence generating the strongest fluorescence intensity. Excitation light interacts with the silver (Ag) nanostructures, inducing resonant oscillation of the electrons on the metal surface, thereby generating a strong local electromagnetic field around the Ag nanoparticles. When the Ag nanoparticles and R6G molecules are at an appropriate distance (10–20 nm), the emission energy of R6G is optimally enhanced due to the surface plasmon resonance effect of Ag. SiO₂ nanospheres acts as dielectric spheres that provide a stable spacing between the Ag nanoparticles and the R6G dye molecules. This ensures efficient excitation energy transfer between R6G and Ag, reaching a maximum when the AgNO₃ concentration is 0.003125 mol/l.

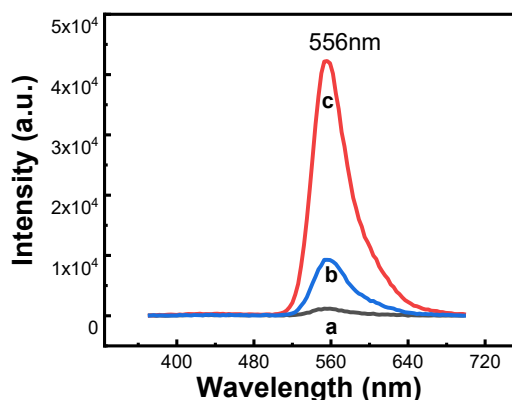


Figure 4. Fluorescence spectra of R6G when using Ag - SiO₂ material: M₁ (a), M₂ (b), M₃ (c).

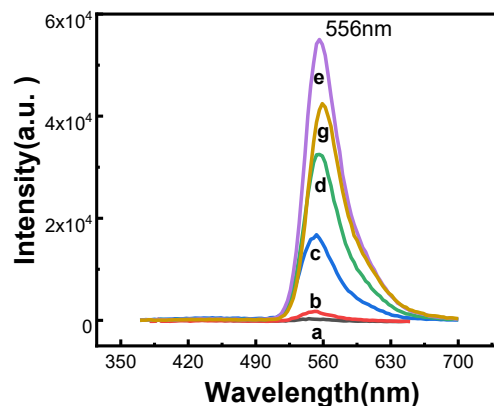


Figure 5. Fluorescence spectra of R6G using Ag - SiO₂ material at R6G concentrations of 0.1 ppm (a), 0.5 ppm (b), 1 ppm (c), 5 ppm (d), 10 ppm (e), and 100 ppm (g).

Figure 5 shows the fluorescence spectra of R6G when using Ag - SiO₂ material with the AgNO₃ concentration of 0.00125 mol/l at R6G concentrations ranging from 0.1 to 100 ppm. The fluorescence spectra show peaks in the range of 551-559 nm, characteristic of the R6G dye. The fluorescence intensity of R6G gradually increases as the concentration rises from 0.1 ppm to 10 ppm, reaching its maximum at 10 ppm, and then decreases at 100 ppm due to the excessively high concentration of R6G. The MEF intensity of R6G using Ag - SiO₂ increased up to 86 times compared with that of not using Ag - SiO₂. In the concentration range from 0.5 ppm to 10 ppm, the fluorescence enhancement effect is strong, but when the concentration reaches 100 ppm, the distance between R6G molecules and Ag nanoparticles becomes too long, leading to a significant reduction in fluorescence intensity. The Ag - SiO₂ material demonstrates the ability to detect and enhance the fluorescence signal of R6G even at very low concentrations, starting from just 0.1 ppm, indicating the high potential for applications in the detection of substances with high sensitivity.

4. Conclusion

The Ag - SiO₂ material was synthesized using chemical reduction and the Stöber method to enhance the fluorescence spectra of R6G dye. The synthesized Ag - SiO₂ nanocomposite material showed that Ag nanoparticles have been decorated on SiO₂ nanospheres. The Ag - SiO₂ material exhibited high quality with well-defined crystal phases, with average sizes of 24 nm and 132 nm for Ag and SiO₂, respectively. Moreover, the as-synthesized Ag - SiO₂ material was able to detect R6G at concentrations ranging from 100 to 0.1 ppm. Using this approach, the fluorescence intensity of R6G at a concentration of 10 ppm increased to 86 times compared with that of only R6G dye.

References

- [1] J. R. Lakowicz, Radiative Decay Engineering: Biophysical and Biomedical Applications: Anal Biochem, Vol. 298, No. 1, 2001, pp. 1-24, <https://doi.org/10.1006/abio.2001.5377>.

- [2] Y. Zhu, K. Morisato, W. Li, K. Kanamori, K. Nakanishi, Synthesis of Silver Nanoparticles Confined in Hierarchically Porous Monolithic Silica: A New Function in Aromatic Hydrocarbon Separations: *ACS Appl Mater Interfaces*, Vol. 5, No. 6, 2013, pp. 2118-2125, <https://doi.org/10.1021/am303163s>.
- [3] J. R. Lakowicz, Plasmonics in Biology and Plasmon-Controlled Fluorescence: *Plasmonics*, Vol. 1, No. 1, 2006, pp. 5-33, <https://doi.org/10.1007/s11468-005-9002-3>.
- [4] M. J. Ahemad, Y. T. Yu, Investigating the Mechanism of Uniform Ag@SiO₂ Core-shell Nanostructures Synthesis by a One-pot Sol-gel Method: *J Solgel Sci Technol*, Vol. 96, No. 3, 2020, pp. 679-689, <https://doi.org/10.1007/s10971-020-05392-y>.
- [5] Y. Wang, X. Wang, W. Ma, R. Lu, W. Zhou, H. Gao, Recent Developments in Rhodamine-Based Chemosensors: A Review of The Years 2018-2022: *Chemosensors* 2022, Vol. 10, No. 10, 2022, pp. 399, <https://doi.org/10.3390/chemosensors10100399>.
- [6] T. Taib, M. R. Johan, W. J. Basirun, Plasmonic SERS Active Nanostructured Ag-SiO₂ at Optimum Volume Ratio Synthesized Via Sol-gel Technique: *Physica B Condens Matter*, Vol. 606, 2021, pp. 412638, <https://doi.org/10.1016/j.physb.2020.412638>.
- [7] N. B. Basosila et al, Biogenic Synthesis, Spectroscopic Characterization and Bioactivity of Cymbopogon Citratus Derived Silver Nanoparticles: *Journal of Applied Sciences and Nanotechnology*, Vol. 3, No. 4, 2023, pp. 33-41, <https://doi.org/10.53293/jasn.2023.7012.1226>.
- [8] D. V. Thai, P. V. Ben, S. C. Doanh, N. T. H. Giang, T. T. Duc, N. T. Dai, B. V. Hong, Synthesis of SiO₂@Ag Nanocomposite for Enhancing Photoluminescence and Raman Characterizations, 2023, <https://doi.org/10.21203/rs.3.rs-3660171/v1>.
- [9] N. Pantelić, C. J. Seliskar, Dynamics of Rhodamine 6G Sorption into a Porous Tri-block Copolymer Thin Film: *Journal of Physical Chemistry C*, Vol. 111, No. 50, 2007, pp. 18595-18604, <https://doi.org/10.1021/jp076274r>.
- [10] M. F. H. A. Kadhemy, K. N. Abbas, W. B. Abdalmuhdi, Physical Properties of Rhodamine 6G Laser Dye Combined in Polyvinyl Alcohol Films as Heat Sensor, *IOP Conference Series, Materials Science and Engineering*, 2020, pp. 928 - 072126.